

The University of Chicago

I. THE PHOTOCHEMICAL POLY-
MERIZATION OF CYANOGEN
II. THE DIFFUSION OF GASES
THROUGH FUSED QUARTZ

A DISSERTATION SUBMITTED TO THE FACULTY
OF THE DIVISION OF THE PHYSICAL SCIENCES
IN CANDIDACY FOR THE DEGREE OF DOCTOR
OF PHILOSOPHY

DEPARTMENT OF CHEMISTRY

By
LIU SHENG T'SAI

Private Edition, Distributed by
THE UNIVERSITY OF CHICAGO LIBRARIES
CHICAGO, ILLINOIS

1932

The University of Chicago

I. THE PHOTOCHEMICAL POLY-
MERIZATION OF CYANOGEN
II. THE DIFFUSION OF GASES
THROUGH FUSED QUARTZ

A DISSERTATION SUBMITTED TO THE FACULTY
OF THE DIVISION OF THE PHYSICAL SCIENCES
IN CANDIDACY FOR THE DEGREE OF DOCTOR
OF PHILOSOPHY

DEPARTMENT OF CHEMISTRY

By
LIU SHENG T'SAI

Private Edition, Distributed by
THE UNIVERSITY OF CHICAGO LIBRARIES
CHICAGO, ILLINOIS

1932



THE PHOTOCHEMICAL POLYMERIZATION OF CYANOGEN

Cyanogen, when heated, forms a solid polymerization product known as paracyanogen, having the empirical formula $(\text{CN})_x$. Its structural formula is unknown, but by analogy with the polymerization products of cyanogen halides¹ it has been assumed that three molecules of cyanogen form one molecule of paracyanogen. Polymerization has been effected not only by heating² but by photochemical means and by bombardment with α -particles³ as well. Berthelot and Gaudechon⁴ carried out the photochemical polymerization in a very qualitative way, and their results gave only the information that the reaction was a photochemical one and that it could be effected by light of convenient frequency. In beginning the more detailed study of this reaction, we found that we were quite unable to reproduce their work, and that the problem was somewhat more difficult of attainment than their results seemed to indicate.

Absorption Measurements

Before beginning the photochemical investigation, it was necessary to obtain information regarding the absorption spectrum of cyanogen. To this end we first employed a Hilger E-2 quartz spectrograph, a hydrogen discharge tube, and a quartz absorption cell 20 cm. long filled with cyanogen at one atmosphere. With the dispersion afforded by this spectrograph we obtained a set of diffuse bands to the short wave length side of about 2230 Å. To determine whether these bands were really diffuse or whether they appeared so through lack of dispersion of our instrument, we made new photographs employing the larger Hilger E-1. This instrument gives a dispersion of approximately 1.5 Å. per mm. in the neighborhood of 2200 Å. Even with this dispersion, which should certainly resolve any bands due to as light a molecule as cyanogen, the bands still appeared diffuse. Using the lines of the copper arc as standards of comparison, the wave lengths of the bands were measured. Table I gives the limits of each of these bands.

The lowest wave length observed corresponds to the limit of transmission of the quartz. It will be observed that there is no regularity in either the width of each band or in their relative positions.

The fact that the absorption bands are diffuse has led us to the conclusion

¹ Mulder, *Rec. trav. chim.*, **5**, 84 (1886); **6**, 199 (1887).

² Troost and Hautefeuille, *Compt. rend.*, **66**, 795 (1868).

³ Lind, Bardwell and Perry, *J. Am. Chem. Soc.*, **48**, 1556, 1575 (1926).

⁴ Berthelot and Gaudechon, *Compt. rend.*, **150**, 1169 (1910).


TABLE I

WAVE LENGTH LIMITS OF THE ABSORPTION BANDS OF CYANOGEN IN ÅNGSTRÖM UNITS

2240-2241	2203-2202	2171-2168
2230-2227	2196-2190	2162-2157
2219-2216	2186-2176	2152-2149
2207-2206.5	2175-2173	2146-2145
2205-2204		

that the primary step in the process is one of predissociation; that the C_2N_2 molecule upon light absorption dissociates. Cyanogen may dissociate on light absorption either into two cyanogen radicals (one may be in the excited state) or into N_2 and C_2 . From our usual conception of the structure of the cyanogen molecule, one would presuppose that the former products rather than N_2 and C_2 would be formed. This is substantiated by the fact that in our later photochemical experiments no evidence of free carbon was found and by the fact that Berthelot and Gaudechon⁴ found neither nitrogen nor carbon as a polymerization product. Furthermore, on passing a weak discharge through cyanogen, only the CN bands were observed.

All the evidence points to the dissociation of cyanogen into CN radicals. The following simple thermochemical calculation will show that such a dissociation is possible

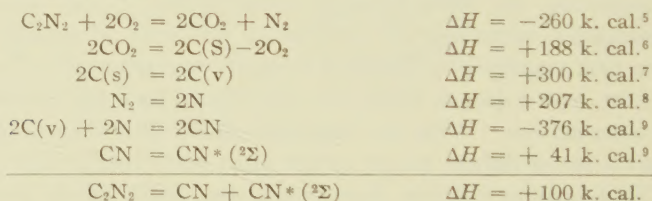

The energy corresponding to the band of the longest wave length observed is 127 k. cal., sufficient to give the products indicated above. A similar calculation shows that this limiting wave length is sufficient to dissociate the cyanogen molecule into normal N_2 and C_2 , but not if one of these products is to be in any one of the known excited electronic states.

Our calculation has shown that the absorbed energy is sufficient to dissociate the C_2N_2 molecule into a normal CN radical and a CN radical either in the $^2\Sigma$ state (3.19 volts) or in the $^2\pi$ state (1.78 volts). The CN radicals in either of these states should give rise to fluorescent radiation if the pressure were such that little damping of that fluorescence took place. Inasmuch as cyanogen absorbs light only very weakly at low pressure, it

⁵ "International Critical Tables," Vol. V, p. 167.

⁶ *Ibid.*, Vol. V, p. 181.

⁷ Kohn and Guckel, *Naturwiss.*, **12**, 139 (1924).

⁸ Mullikan and Birge, *Nature*, **122**, 844 (1928).

⁹ Villars, *J. Am. Chem. Soc.*, **52**, 61 (1930).

would hardly be expected that such a fluorescence could be detected and, in fact, all efforts to obtain any trace of fluorescence were in vain. We employed as a light source a zinc spark, a cadmium spark and a hydrogen discharge tube and in all cases the pressure of the absorbing gas was in the neighborhood of 1 mm. This pressure we guessed to be about an optimum one in view of the small absorption of this gas, and the maximum damping pressure of others. Using the Steinheil spectrograph ($f = 2.8$), with several exposures of six to twelve hours each we obtained no trace of a fluorescence spectrum.

The fact that no fluorescence was obtained does not argue against the assumption that one of the CN radicals is left in an excited state. Were the absorption as great as that of iodine, one might use such an argument, but in this case the absorption is considerably less.

The wave length of the effective light was such that in our photochemical experiments we were unable to use a monochromator but the range was so narrow (2240–2145 Å.) that this was unnecessary. We could without any appreciable error assume a mean effective wave length of 2150 Å. We did not therefore determine wave lengths but rather determined the total absorption in the same cell that was used in the photochemical experiments.

The variations in intensity of the light source used in the absorption measurements (described later) and the unsteadiness of the thermopile circuit were large enough so that we could not with assurance use the usual method of measuring the light intensity with a full and empty cell alternated in the light path. We found that the following method gave reproducible results.

The absorption cell was a cylindrical tube 25 mm. long and 2 cm. in diameter with quartz windows at each end. This tube was connected with an intervening stopcock to a liter bulb which in turn was connected to a mercury reservoir. Acting similarly to a Töpler pump, the gas in the one-liter bulb could be compressed into the absorption cell and the stopcock closed. The one-liter bulb could be evacuated by lowering the mercury reservoir and then upon opening the stopcock the gas could be expanded to about 125 times its initial volume and the pressure reduced correspondingly.

The procedure then was to have the light from the hydrogen discharge tube pass through the absorption cell full of gas and onto the thermopile. When the galvanometer in the thermopile circuit was exceptionally steady, the stopcock was opened, the gas in the cell expanded, and the deflection of the galvanometer noted. In all the absorption measurements the gas was at a pressure of one atmosphere in the absorption cell. When the stopcock was opened, the gas remaining was at a pressure of about 6 mm., and this latter pressure we considered to be ineffective in our calculations.

The result of ten individual experiments gave an absorption of 8.8 (± 0.6) % of the total radiation passing through the cell.

Determination of Quantum Efficiency

Preliminary experiments with the quartz mercury vapor lamp, the cadmium spark, the zinc spark and the hydrogen discharge tube as light sources showed that only the latter could be used effectively in this experiment.

Berthelot and Gaudechon obtained an 18.5% contraction in volume when cyanogen was subjected to the radiation of a quartz mercury vapor lamp. Repeating this work and loading our lamp to its full capacity, we were unable to obtain any appreciable volume contraction in this time. A consideration of the emission spectrum of the mercury lamp and the absorption spectrum of cyanogen makes it improbable that such an effect should be observed when pure cyanogen was used, since there are no emission lines in the region of absorption. The same is true for the cadmium spark. The spectrum of the zinc spark shows strong lines below the limit of absorption, but these were apparently not of sufficient intensity after passing

through the quartz window, or they occurred in a region of no absorption. Lacking details we cannot venture any explanation of Berthelot and Gaudechon's positive results other than that their cyanogen contained some sensitizing agent.

The hydrogen discharge tube was a modification of the one described by Lawrence and Edlefsen.¹⁰ Instead of using sealing wax to join the quartz tube to the Pyrex electrode cylinders, we used a quartz-Pyrex seal as shown in Fig. 1. The current was supplied through a 6600 volt 25 k. v. a.

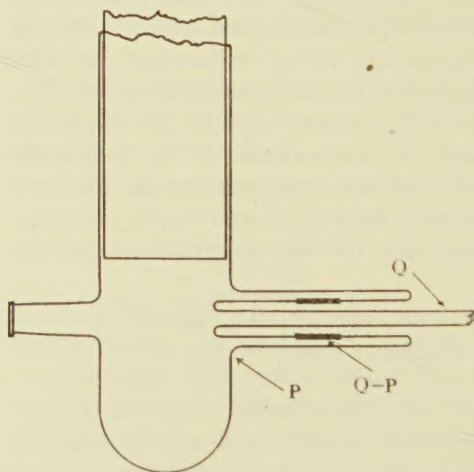


Fig. 1.—P, Pyrex; Q, quartz; Q—P quartz-Pyrex seal.

transformer equipped with a resistance in the primary circuit. The usual operating voltage and current through the tube were 3000 volts and 5 to 6 amperes, respectively. With this load the tube usually broke down at the end of about two weeks of running.

The cyanogen used in all these experiments was prepared by heating recrystallized silver cyanide in a previously evacuated line. Before being used the gas was dried over phosphorus pentoxide and purified by three fractionations.

The decrease in the amount of cyanogen in any single run was so small

¹⁰ Lawrence and Edlefsen, *Rev. Sci. Instr.*, **1**, 45 (1930).

that we were unable to employ the usual manometric method with mercury as the manometer medium. We had to resort, therefore, to the use of some organic liquid as the manometer medium, employ a tilted mercury manometer, or use a horizontal tube containing a bead of mercury. The last two methods have the disadvantage that the mercury tends to stick to the sides of the tube but since cyanogen is slightly soluble in organic liquids and since the rate of pressure decrease was so small, we adopted the last-named method, *i. e.*, the horizontal tube holding a bead of mercury. When precautions were taken to have the capillary tube very clean and the mercury very pure, and with continual tapping of the tube, consistent results were obtained. The apparatus used to determine the rate of volume decrease was nothing more than the cell used in the absorption measurements connected to the capillary as a side tube. This tube was placed in the path of the light beam near the discharge tube and the thermopile immediately behind it. The cell was shielded and its temperature at all times known by means of Beckmann thermometers.

As the reaction proceeded, the polymer formed as a faint cloud and settled to the bottom of the tube. Unfortunately some of the polymer gathered on the end windows and only the first part of each run could be used for our calculation. Knowing the rate of volume decrease and the light intensity, and after integrating the intensity over the cross section of the light beam and calibrating the thermopile against a standard lamp, we were able to calculate the quantum efficiency. Table II gives the results of six runs.

TABLE II
QUANTUM EFFICIENCY OF POLYMERIZATION OF CYANOGEN

Run	Length of run, min.	No. of molecules of (CN) ₂ polymerized	No. of quanta absorbed	Moles per einstein
1	21	5.8×10^{17}	2.22×10^{17}	2.6
2	25	10.1×10^{17}	3.28×10^{17}	3.1
3	18	6.4×10^{17}	2.74×10^{17}	2.4
4	22	8.9×10^{17}	3.02×10^{17}	3.0
5	24	10.6×10^{17}	2.68×10^{17}	3.0
6	25	9.7×10^{17}	2.9×10^{17}	3.3

Av. 3.0^a

^a One run gave a value of 4.6 moles per einstein for the quantum efficiency. Since this value deviated from the mean to a much larger extent than the others (over 50%) we have felt justified in omitting this from the table.


In the calculation we have used 2150 Å. as the mean wave length. This mean was selected by an examination of the photograph of the absorption spectrum.

The paracyanogen was distinctly brown in color. Upon heating it *in vacuo* the product volatilized, leaving no solid residue.


Since there was some mercury vapor present in our cell, the question might naturally arise as to the possibility of photochemical sensitization by the mercury. To test this we made a run with the mouth of a small flask of boiling mercury just under the path of the beam between the discharge tube and the absorption cell. There was no apparent difference between the polymerization rates with and without the intervening mercury vapor. The reaction in our case, therefore, was not due in any appreciable extent to a sensitized reaction.

Discussion

The low quantum efficiency obtained for this reaction precludes any long chain reaction accounting for the mechanism of polymerization. As the first step of the mechanism we feel that the evidence given by the diffuse bands and the lack of free carbon points to a dissociation into CN radicals.



The simplest mechanism to account for a quantum efficiency of three moles per einstein would have as the second step



The last product could, if unstable, then form a larger group by secondary polymerization.

Although we have obtained only diffuse bands in the absorption spectrum, Henri¹¹ in a table in his "Structure des Molecules" gives a region of fine structured bands from 2385 to 2200 Å. With a tube 20 cm. long filled with cyanogen to one atmosphere pressure we did not detect the faintest trace of these bands. We can only surmise that Henri's cyanogen contained some foreign matter. The same, we suspect, applies to the work of Berthelot and Gaudechon, since cyanogen does not absorb any of the lines of the quartz mercury vapor lamp.

Lind, Bardwell and Perry³ in their work on the polymerization of cyanogen by α -particles found that about seven molecules polymerized per ion pair. The mechanisms in their case and that in ours are apparently different. There is no reason to suppose that these mechanisms should be the same in the two cases, particularly since no long chain reaction is involved. These authors described their product as a black polymer. The product in our case was distinctly brown. This difference, however, might easily be accounted for by the small side reaction liberating nitrogen, which these authors found.

Summary

1. The absorption spectrum of cyanogen consists of a series of diffuse bands extending from 2240 Å. to the limit of transmissivity of quartz.

¹¹ V. Henri, "Structure des Molecules," J. Hermann et Cie, Paris, France, p. 99.

2. The conclusion is drawn that upon absorption of light between 2145 and 2240 Å., cyanogen dissociates (predissociation) into either two normal CN radicals or one normal and one excited.

3. No cyanogen fluorescence was obtained.

4. The quantitative absorption of light by cyanogen in the region 2145 to 2240 Å. was determined.

5. The quantum efficiency for the photochemical reaction $(\text{CN})_2 \longrightarrow$ paracyanogen was determined to be three moles per einstein.

6. A brief discussion of the mechanism, together with a discussion of the results of other investigators on the polymerization of cyanogen, concludes the work.

THE DIFFUSION OF GASES THROUGH FUSED QUARTZ

BY LIU SHENG T'SAI

In 1900 Villard¹ first observed that fused quartz, when heated to redness, was permeable to hydrogen. This observation was followed by a number of investigations²⁻¹³ on the diffusion of hydrogen, helium, neon, argon, oxygen, and nitrogen through fused silica and through various kinds of glass. Quantitative measurements of permeabilities for gases other than hydrogen and helium have not been made, and some of the qualitative observations are in disagreement.

Williams and Ferguson⁹ found that with gas pressures up to one atmosphere, and temperatures to 881°C no leakage of air or nitrogen gas through silica glass was observed. Berthelot observed that both oxygen and nitrogen were present in an evacuated tube after heating in air for half an hour at 1300°C., while Wustner⁷ found that nitrogen diffused through quartz at 900°C and 1,000 atmospheres, and that under approximately the same conditions, oxygen did not. Mayer's⁶ observations showed that for pressures smaller than atmospheric neither oxygen nor nitrogen diffused through quartz, while for pressures greater than atmospheric this experimenter found an increase in diffusion with increase in pressure and temperature.

Williams and Ferguson and Van Voorhis also found that the silica glass is permeable to helium, and is easily observable at 180°C. The permeability is proportional to gas pressure, and, according to the former of these observers, is an exponential function of the temperature.

Richardson and Richardson⁴ observed that neon diffused through quartz at about 1000°C. After one hour's heating in air a faint blue argon spectrum and a yellow helium line were obtained, while prolonged heating resulted in the more fully developed spectra of both helium and neon. The argon spectrum, they concluded, was due to the trace of air absorbed by the wall of the tube before heating.

In preparation for later experiments it was found desirable to have better data on the permeability of quartz glass for some of these gases, so we have undertaken quantitative determinations of this property.

Apparatus and Experimental Procedure

The diffusion cell consisted of a thin tube of clear fused quartz, the thickness of which was measured by three different methods: (1) measurement with calipers, (2) calculation of the thickness from the weight of water displaced by the quartz tube, the density and the area of the immersed portion of the quartz tube being known, (3) by the same method as (2) except that mercury was used instead of water. The average of these measurements gave a thickness of 0.033 cm. After the thickness had been determined the tube

was sealed off at one end and at the other end it was sealed to a quartz capillary which was in turn connected to the McLeod gauge through a quartz-pyrex graded seal. Around the cell, which had the dimensions of 1.46 cm outside diameter by 16 cm, a heavy-wall quartz test tube was fitted to hold the gas. To ensure the air-tightness of the necessary glass-rubber connection, which was of such length that it was far away from the furnace, DeKhotinsky cement was used. In addition, an electric fan was used to facilitate the cooling.

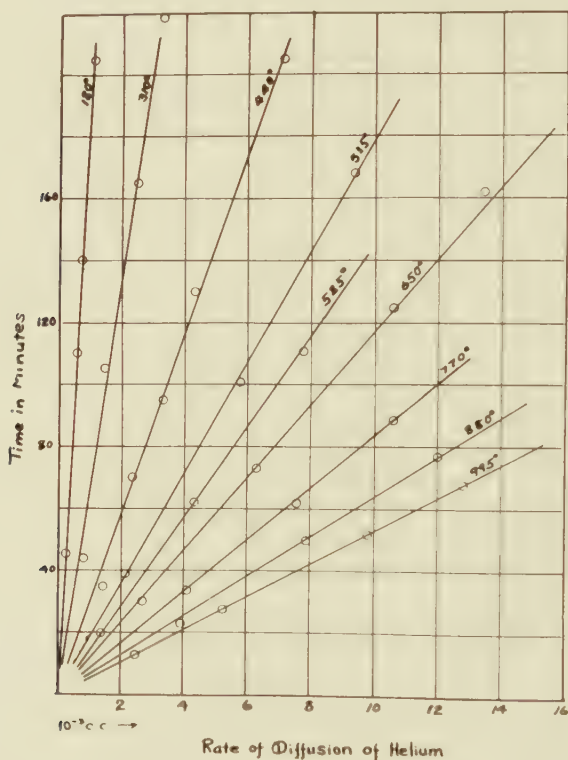


FIG. 1

After the apparatus was set up the whole system was evacuated for about three days. At the end of this time the pressure in the apparatus was less than 1×10^{-6} mm but on standing for about twelve hours the pressure increased to about 2×10^{-4} mm. The casing was then evacuated and the gas in question was introduced. The system was evacuated during the time that it took for the furnace to reach temperature equilibrium, about three hours, after which time the pump was disconnected and the measurements were begun. The increase in pressure was determined with a McLeod gauge at regular intervals of time, and such results as were obtained for neon and helium are shown in Figs. 1 and 2. As has been noted, there was a slight increase of pressure with time due to the desorption of the gas from the glass

walls. It was, therefore, necessary to make this correction for the gases which diffuse rather slowly. This was done by noting the rate of increase of pressure of the system while the cell was at the temperature under investigation and the casing evacuated. The difference between the apparent rate obtained in the usual manner, and this blank rate gave the actual rate due to diffusion. When these corrections were taken into consideration no definite diffusions were observed for nitrogen, oxygen, and argon. In the case of argon, spectroscopic tests showed that diffusion of this gas took place at the highest temperatures, but that the rate was not enough to offer any quantitative data.

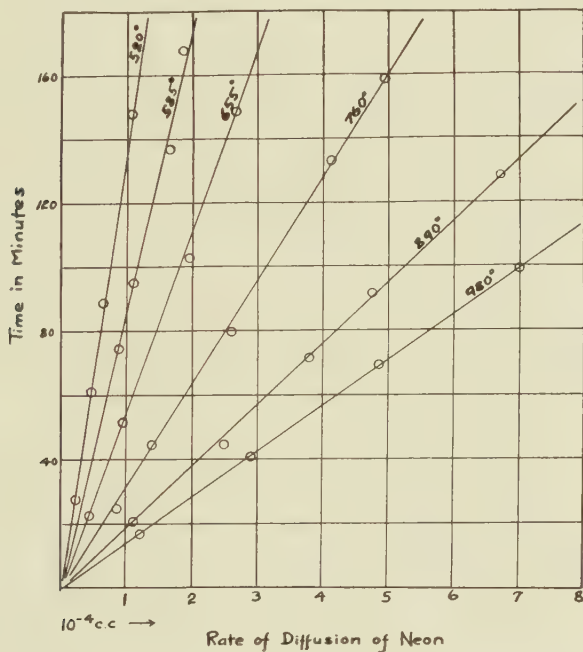


FIG. 2

Preparation of Materials

Helium was supplied in a pure form by the United States Bureau of Mines, and was used without further purification.

Neon, supplied by the Air Reduction Company, was purified three times by fractional condensation with activated charcoal at liquid air temperature. Any helium present in the original neon was removed in this way.

Argon, supplied by the same company, was used without purification.

Oxygen was prepared by heating potassium chlorate and manganese dioxide. The gas was led through a phosphorus pentoxide tube before using.

Nitrogen was prepared by heating a solution of sodium nitrite and ammonium chloride. The gas was purified by passing it through a tube containing dry potassium hydroxide and then over phosphorus pentoxide.

Discussion of Results

Permeability is here defined as the rate in cubic centimeters (measured at 0°C and 760 mm) per hour at which the gas at one atmosphere pressure diffuses into vacuum through a wall 1 mm thick and 1 square centimeter in area. Table I shows the permeability of quartz glass for both helium and neon at different temperatures. The calculation of these values was made by assuming that the rate of diffusion is inversely proportional to the thickness of the wall, an assumption which, according to the mathematical formulation

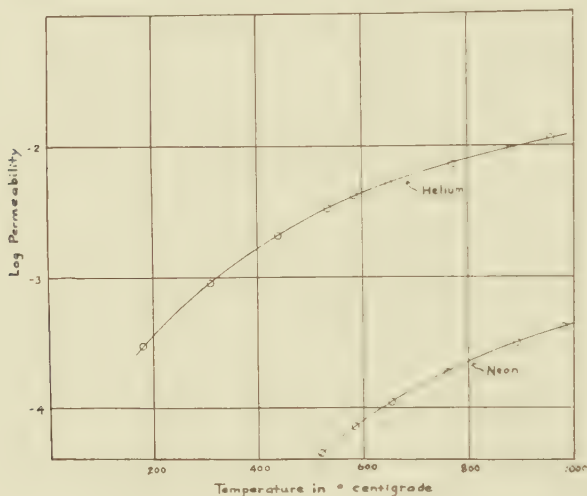


FIG 3

of the simple theory of diffusion, is a valid one for thin walls.⁷ The plot of the logarithms of the permeability against temperature for these two gases is shown in Fig. 3.

In as much as the permeability of glass increases very rapidly with the temperature, it has been assumed that this function is an exponential one. Williams and Ferguson, from measurements at three temperatures, concluded that in the case of helium such an exponential relationship existed. More observations, however, were necessary to indicate the real trend of the curve. Our results show that the increase in permeability with temperature is somewhat less than that which the exponential relationship demands. For the permeability of helium at 440° and at atmospheric pressure, Williams and Ferguson obtained a value of 3.0×10^{-4} cc, Van Voorhis, approximately 25×10^{-4} cc, while we get a value of 21×10^{-4} cc. As shown by these authors, different samples of silica glass gave different values of the permeability for hydrogen, so we do not expect a better check than this. The permeabilities for helium and neon at 900°C and atmospheric pressure are 100×10^{-4} and 3.2×10^{-4} , or in the ratio 31 to 1, respectively. Williams and Ferguson found a ratio of 22 to 1 for helium and hydrogen at 500°C and 760 mm.

TABLE I

Permeability for Helium

Temperature	Permeability $\times 10^4$	Log Permeability
180°C	3	-3.523
310	9	-3.046
440	21	-2.678
535	33	-2.482
585	42	-2.377
650	51	-2.293
770	72	-2.143
880	94	-2.027
955	113	-1.947

Permeability for Neon

520°C	.45	-4.347
585	.70	-4.155
655	1.10	-3.959
760	1.85	-3.733
890	3.15	-3.502
980	4.20	-3.377

If the increasing permeability with increasing temperature were due solely to the increased velocity of the permeating molecules one would expect the permeability to increase as the square root of the temperature. This is very far from the case. The quartz glass must be regarded as possessing channels¹⁴ which increase in clearance with increasing temperature. As shown by X-ray analysis,¹⁵ silica glass, when heated for thirty minutes at 700°C, undergoes marked devitrification. This undoubtedly increases the channels for the diffusing gas, increasing the permeability. We found that silica glass, when heated to high temperatures, undergoes a permanent change which results in a noticeably greater permeability for helium. Since different samples of quartz glass give slightly different results, and since the permeability depends somewhat upon the previous heat treatment of the glass, the absolute values we give here are for one particular sample only, and cannot be applied too exactly in other calculations.

As one would expect, the permeability of quartz glass for various gases is greater for the atoms or molecules of smaller cross section. Our positive result for argon is undoubtedly real but the value of the permeability of quartz for this gas was so low that its measurement was impossible. The heavier rare gases would undoubtedly diffuse so slowly as to prohibit detection, if any diffusion at all took place.

References

- ¹ Villard: Compt. rend., **130**, 1752 (1900).
- ² Jaquerot and Perrot: Compt. rend., **139**, 789 (1905).
- ³ Berthelot: Compt. rend., **140**, 821 (1905).
- ⁴ Richardson and Richardson: Phil. Mag., **22**, 704 (1911).
- ⁵ Bodenstein and Kranendieck: Nernst Festschrift, 100 (1912).
- ⁶ Mayer: Phys. Rev., **6**, 283 (1915).
- ⁷ Wustner: Ann. Physik, **46**, 1095 (1915).
- ⁸ Cardoso: Science Abstracts, **25A**, 732.
- ⁹ Williams and Ferguson: J. Am. Chem. Soc., **44**, 2160 (1922).
- ¹⁰ Piutti and Lera: Men. Accad. Lincei, (v) **14**, 125 (1923).
- ¹¹ Elsey: J. Am. Chem. Soc., **48**, 1600 (1926).
- ¹² Van Voorhis: Phys. Rev., (A) **23**, 557 (1925).
- ¹³ Baxter, Starkweather, and Ellestad: Science, **68**, 516 (1928).
- ¹⁴ Zachariason: Work to be published in the J. Am. Chem. Soc.
- ¹⁵ Randall, Rooksby, and Cooper: Krist., **75**, 707 (1930).

*George Herbert Jones Laboratory,
University of Chicago.*

